


Discovery of FeBi₂

James P. S. Walsh,[†] Samantha M. Clarke,[†] Yue Meng,[‡] Steven D. Jacobsen,[§] and Danna E. Freedman^{*†}[†]Department of Chemistry, Northwestern University, Evanston, Illinois 60208, United States[‡]HPCAT, Geophysical Laboratory, Carnegie Institution of Washington, Argonne, Illinois 60439, United States[§]Department of Earth and Planetary Sciences, Northwestern University, Evanston, Illinois 60208, United States

Supporting Information

ABSTRACT: Recent advances in high-pressure techniques offer chemists access to vast regions of uncharted synthetic phase space, expanding our experimental reach to pressures comparable to the core of the Earth. These newfound capabilities enable us to revisit simple binary systems in search of compounds that for decades have remained elusive. The most tantalizing of these targets are systems in which the two elements in question do not interact even as molten liquids—so-called immiscible systems. As a prominent example, immiscibility between iron and bismuth is so severe that no material containing Fe–Bi bonds is known to exist. The elusiveness of Fe–Bi bonds has a myriad of consequences; crucially, it precludes completing the iron pnictide superconductor series. Herein we report the first iron–bismuth binary compound, FeBi₂, featuring the first Fe–Bi bond in the solid state. We employed geologically relevant pressures, similar to the core of Mars, to access FeBi₂, which we synthesized at 30 GPa and 1500 K. The compound crystallizes in the Al₂Cu structure type (space group *I4/mcm*) with *a* = 6.3121(3) Å and *c* = 5.4211(4) Å. The new binary intermetallic phase persists from its formation pressure of 30 GPa down to 3 GPa. The existence of this phase at low pressures suggests that it might be quenchable to ambient pressure at low temperatures. These results offer a pathway toward the realization of new exotic materials.

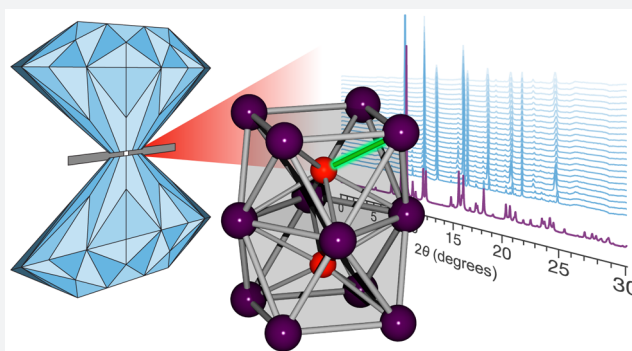

INTRODUCTION

Creating and understanding new bonding interactions is central to chemistry; each new bond gives rise to undiscovered electronic structure and provides novel insight into chemical bonding in materials. Thousands of unique chemical interactions are known, and yet within the periodic table there remain bonds that are counterintuitively absent. This is particularly enigmatic when the two elements in question exhibit a diverse chemistry with other elements across the periodic table. For chemists, such systems represent unexplored regions of phase space with tremendous potential for discovery; iron–bismuth is a prominent example of such a system. Indeed, the immiscibility of the elements is so severe that there have been no reports of Fe–Bi bonds in the solid-state literature. This is particularly intriguing from a chemical standpoint because there are numerous applications that would benefit from the creation of this interaction, notably magnetism and superconductivity.

Our interest in the intersection of iron and bismuth arises from the potential for transformative magnetic properties. By fusing the paramagnetism of iron with the spin–orbit coupling inherent to bismuth, we envision the creation of a new family of magnetic materials. Creating an iron–bismuth bonding interaction is also of urgent interest to the superconductivity community, where iron–bismuth interactions are a prerequisite

to create the missing members of the iron pnictide family of superconductors.¹ Creating new bismuth superconductors could provide crucial insight into the mechanism of these exotic iron-based materials. Despite over a decade of focused interest within this area, iron–bismuth bonds remain elusive within solid-state materials.

One key challenge in creating an iron–bismuth interaction is the immiscibility of the two elements. Even at the elevated temperature of 1873 K, where both metals are in the liquid state, the solubility of bismuth in iron is only 0.16 wt %.² This suggests that extreme conditions may be required to access a binary compound. Toward that end, we considered the application of geologically relevant pressures. Bismuth is unusually well-suited to high-pressure synthesis due to its numerous high-pressure phases and associated structural transformations.^{3,4} Indeed, recently, high pressure was employed as a vector to access new binary compounds in bismuth systems that were previously devoid of intermetallic phases, including CoBi₃⁵ and Cu₁₁Bi.⁶ Both of these compounds are the first structurally characterized intermetallic phases in their respective binary systems,^{7,8} and both were synthesized by reaction of the elements at high-pressure

Received: September 25, 2016

Published: October 26, 2016

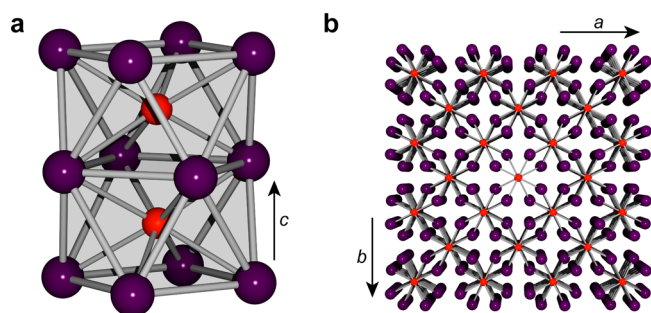


Figure 1. Crystal structure of FeBi_2 determined at 29.9(1) GPa. Purple and orange spheres represent Bi and Fe, respectively. (a) View of two face-sharing $\{\text{FeBi}_8\}$ square antiprisms stacking along the c -direction. (b) View down the c -axis showing the edge-sharing linkages formed between the stacked columns.

conditions (4–6 GPa) using a large volume press (LVP). We hypothesized during our research on the $\text{Cu}_{11}\text{Bi}_7$ system that the mutual solubility of the Cu and Bi enabled its facile synthesis at relatively low pressures.

Given the immiscibility of elemental iron and bismuth, even in the molten state (Figure S1),⁹ we postulated that we would require access to a significantly higher pressure regime in order to create the first iron–bismuth binary compound. Toward that end, we employed a diamond anvil cell (DAC), which permits *in situ* structural and physical characterization over a much wider range of pressure–temperature space than can be achieved in the LVP. Indeed, DACs are capable of pressures well beyond 250 GPa, which is over an order of magnitude higher than the maximum pressures achievable in LVP reactions. To contextualize this increase in pressure, while our previous synthesis of $\text{Cu}_{11}\text{Bi}_7$ was performed at pressures comparable to the core of the Moon (~ 6 GPa), these experiments at ~ 30 GPa are performed at pressures comparable to the core of Mars.¹⁰

Herein we report the synthesis of the first iron–bismuth binary compound, FeBi_2 (Figure 1), via pressurization in a DAC at 30 GPa and laser-heating to 1500 K. Decompression studies demonstrate that the material retains the Al_2Cu structure type down to at least 2.9(1) GPa, suggesting that it might be possible to quench the phase to ambient pressures at low temperatures.

RESULTS AND DISCUSSION

We targeted the synthesis of a novel iron–bismuth binary at pressures between 12–40 GPa using a DAC (see Supporting Information for full details). We performed reactions within this pressure range to ensure that iron would be present as ϵ -Fe (*hcp*), the high-pressure phase of Fe, since our prior reactions at lower pressures—where iron is in the α -Fe (*bcc*) phase—were unsuccessful. The experiment was monitored by continuous *in situ* powder X-ray diffraction (PXRD) during laser heating of an iron and bismuth mixture inside a DAC, which allows for the real-time visualization of phase formation as the reaction takes place. This remarkable capability facilitates the exploration of pressure–temperature phase space for a given composition, and also aids in the optimization of the experimental procedure. We employed MgO as a thermal insulator between the sample and the diamond anvils during the laser heating, and also as a pressure-transmitting medium. Fortuitously, its well-defined equation of state also enabled its use as a precise pressure calibrant at the reaction site.¹¹

We heated pressurized samples of elemental iron and bismuth using a microfocused infrared laser (fwhm = 40–80 μm) while performing *in situ* PXRD at beamline 16-ID-B, HPCAT, Advanced Photon Source (APS). Between 12 and 30 GPa, we did not observe the formation of any novel phases during heating, even up to 2000 K. However, at pressures above 30 GPa, and upon heating to approximately 1500 K, peaks belonging to a new phase began to appear in the diffraction pattern. These peaks grew in intensity for about 4 min, at which point no further changes were observed. We then switched off the laser heating to thermally quench the reaction. The reaction can be reproduced successfully by pressurizing iron and bismuth in the range of 30–35 GPa and heating at or above ca. 1500 K (see the Supporting Information for details).

Examination of the diffraction patterns acquired at high pressure reveals four phases: MgO (*fcc*), Bi(V) (*bcc*), ϵ -Fe (*hcp*), and a new phase. The observation of a high quality MgO diffraction pattern enables us to employ it as a pressure calibrant by studying the change in lattice parameters at pressure. By placing the compressed MgO lattice parameters into its well-described equation of state, we can determine that the initial pressure before heating was 32.2(1) GPa, and fell to 29.9(1) GPa after thermal quenching.

The *in situ* PXRD experiments at the synchrotron source offered sufficient resolution to enable the simultaneous modeling of all four phases using the TOPAS software package (Figure 2).¹² The gradual appearance of the new phase over a 4 min time window enabled us to easily isolate and index its associated peaks. The relatively small number of peaks in the diffraction pattern was indicative of a high symmetry crystal system, which we indexed to the tetragonal space group, $I4/mcm$. A search of known binary structure types with this space group yielded the Al_2Cu structure type, in which several iron binary compounds crystallize.^{13–15} The new phase was well modeled with Rietveld refinement as FeBi_2 in the Al_2Cu structure type, with lattice parameters of $a = 6.3121(3)$ Å and $c = 5.4211(4)$ Å (at 29.9(1) GPa). The early transition metal–antimonides, TiSb_2 ¹⁶ and VSb_2 ,^{17,18} crystallize within the same Al_2Cu structure type at ambient pressures, while CrSb_2 and

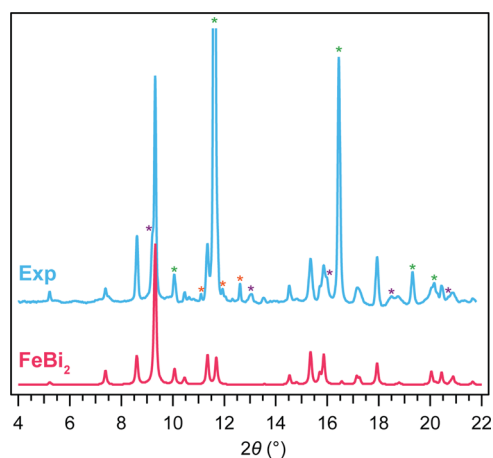


Figure 2. Background-subtracted X-ray diffraction pattern of the reaction site after cooling to room temperature ($\lambda = 0.406626$ Å, $P = 29.9(1)$ GPa). The experimental trace is plotted in blue, with asterisks denoting the peaks arising from MgO (green), unreacted Bi(V) (purple), and unreacted ϵ -Fe (orange). The simulated pattern of FeBi_2 based on the final fit parameters is plotted in pink.

FeSb₂ undergo a pressure-induced transition from the marcasite FeS₂ structure type into the Al₂Cu structure type at pressures of 5.5 GPa¹⁹ and 14.3 GPa,¹³ respectively. FeBi₂ can therefore be considered as a structural analogue of the high-pressure phase of FeSb₂.

The structure of FeBi₂ is composed of iron atoms coordinated by eight bismuth atoms to form square antiprisms with the C₄ axes parallel to the unit cell *c*-axis (Figure 1a). The square faces are not perfectly staggered, with an angle of 37.5(1)° between them. This structure is reminiscent of the recently isolated ternary cluster anion [Ni₂Sn₇Bi₅]³⁻, which features a 12-atom Sn/Bi cage surrounding two nickel atoms.²⁰ In FeBi₂, the {FeBi₈} square antiprisms share both of their square faces with adjacent antiprisms to form columns along the *c*-direction (Figure 1a), and these columns share edges with neighboring columns throughout the *ab*-plane (Figure 1b). At 30 GPa, the eight Fe–Bi interactions around each iron atom are equivalent by symmetry, with interatomic distances of 2.719(2) Å. For comparison, molecular Fe–Bi bonds are known to exist in iron carbonyl species, where they possess lengths up to 2.85 Å.^{21–23} The sum of the covalent radii of iron and bismuth is 1.25 Å (*r*_{Fe}) + 1.46 Å (*r*_{Bi}) = 2.71 Å,²⁴ which compares very well with the value obtained for Fe–Bi in FeBi₂ at the formation pressure. We should note that covalent radii may underestimate bond lengths in intermetallic compounds, due to the increased electron delocalization across the structure coupled with the larger number of interactions common in intermetallic compounds, as compared with the highly directional interactions found in molecules. However, these numbers are still useful as a first approximation of bonding distances in intermetallic compounds. The shortest Fe–Fe distances in FeBi₂ are those along the *c*-axis, 2.7107(3) Å, which is longer than the Fe–Fe distance found in high-pressure FeSb₂, (2.536 Å at 28.2 GPa),¹³ but shorter than those featured in the Al₂Cu-type compound FeZr₂, 2.798(2) Å.¹⁵

There are three unique Bi–Bi interactions within each antiprism: one that forms the edges of the square faces, 3.333(2) Å, and two that form the sides of the triangular faces that connect the upper and lower square faces in each prism, 3.106(3) Å and 3.419(3) Å. An even shorter Bi–Bi interaction exists between bismuth atoms on adjacent antiprism columns (Figure 3), with a distance of 2.948(5) Å. The large range of distances for the Bi–Bi bonds led us to further examine the nature of these interactions. The shortest Bi–Bi distance of 2.948(5) Å is quite short for a Bi–Bi bond, indicating that the interaction is higher order than that of a single Bi–Bi bond. Although high pressure may contribute to the bond contraction, it is worthwhile to note that the single Bi–Bi bond in elemental Bi(V) at 30 GPa is significantly longer (3.1044(3) Å) than the distance seen here. Indeed, the short Bi–Bi bond in FeBi₂ is reminiscent of the Bi₂ dimer found in the alkali metal–bismuthide binaries, such as Cs₃Bi₂, 2.976(2) Å, and K₃Bi₂, 3.014 Å,²⁵ and in the transition metal–bismuth intermetallic compounds, PtBi₂²⁶ and RhBi₂.²⁷ Within these compounds, a Bi₂²⁻ species, with an extra electron delocalized within the structure, is commonly invoked to understand the electronic structure. The frequently observed Bi–Bi structural motif suggests that this proximal interaction may be important in the formation of this structure. Indeed, there are a number of molecular species featuring a similarly short Bi–Bi bond,^{28–33} indicating that this may be a crucial stabilizing factor. As the pressure is released, this Bi–Bi bond distance elongates to

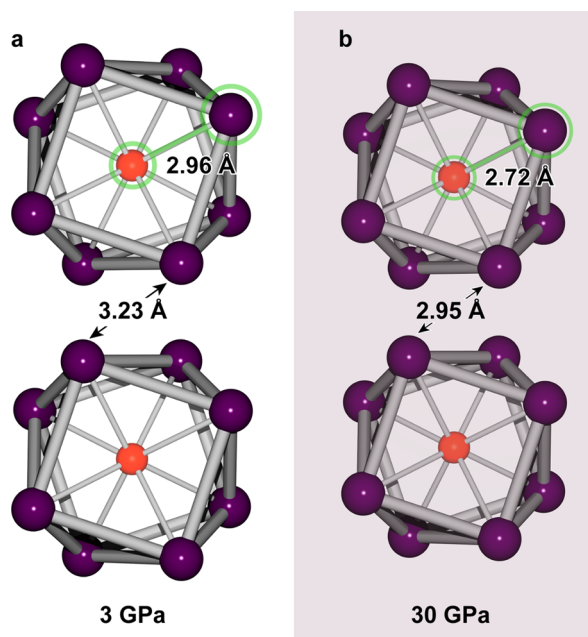


Figure 3. View down the *c*-axis at 3 GPa (a) and 30 GPa (b), illustrating the effect of increased pressure on the Fe–Bi interaction and the intercolumn Bi–Bi interaction. Purple and orange spheres represent Bi and Fe atoms, respectively.

3.2270(4) Å at 3 GPa, indicating that the stabilizing influence of this dinuclear interaction has diminished (Figure 3).

Compounds displaying long-term stability under ambient conditions after high-pressure synthesis are referred to as quenchable. In order to assess whether the structure could be quenched to ambient pressures, we incrementally decompressed a sample of FeBi₂. Rietveld refinement of PXRD patterns collected after each decompression step shows a smooth change in the unit cell parameters of FeBi₂ as the pressure is released (Figure 4). Peaks belonging to the FeBi₂ phase were evident down to 2.9(1) GPa, but were no longer present upon the final decompression to 0.5(1) GPa, indicating that the compound either decomposed or lost crystallinity.

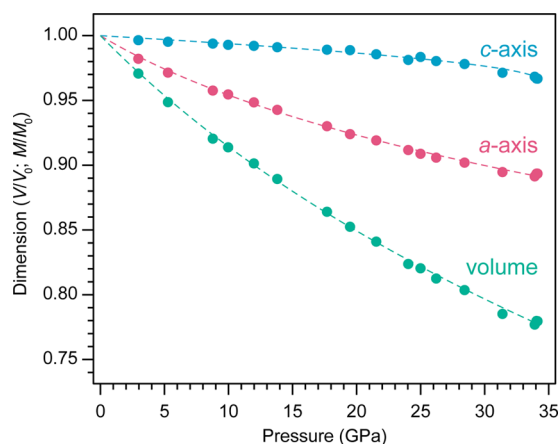


Figure 4. Experimental pressure dependence of the normalized unit cell parameters upon decompression of FeBi₂. Dashed lines are fits of the experimental data using the third-order Birch–Murnaghan isothermal equation of state, as described in the Supporting Information.

Completing the iron pnictide series of compounds enables us to gain insight into the structural properties of these materials. First-principles calculations carried out on the known Al_2Cu structure type iron pnictides, FeP_2 , FeAs_2 , and FeSb_2 , suggest a decrease in compressibility as the reference volume (V_0) increases.³⁴ Specifically, there is an inverse linear relationship between V_0 (145.2 \AA^3 , 177.4 \AA^3 , and 237.0 \AA^3 , respectively) and the bulk modulus, B_0 (153, 109, and 68 GPa, respectively), for this family of compounds. In order to evaluate the compressibility of FeBi_2 , we fit the evolution of the FeBi_2 lattice parameters (Table S6) as a function of pressure with a third-order Birch–Murnaghan isothermal equation of state (BM3) using the software package EosFit-7c.³⁵

For FeBi_2 , we obtain $V_0 = 273(3) \text{\AA}^3$, $B_0 = 99(5) \text{ GPa}$, and $B'_0 = 2.7(2)$. Using a second-order fit ($B'_0 = 4$ implied), we obtain $V_0 = 278(1) \text{\AA}^3$ and $B_0 = 75(2) \text{ GPa}$. If we compare the BM3 values to those reported for FeSb_2 , which is a close structural analogue to FeBi_2 , we find that FeBi_2 is roughly 45% more incompressible than FeSb_2 . If the trend of increasing compressibility were to continue upon moving down the iron pnictide series, then $V_0 = 273(3) \text{\AA}^3$ would lead to an expected value of $B_0 \simeq 49 \text{ GPa}$ for FeBi_2 . Since we actually observe a decreased compressibility in FeBi_2 compared to FeSb_2 , this trend does not appear to extend to the bismuthides. We hypothesize that this unexpected result could stem from the increased importance of relativistic effects in bismuth,³⁶ which are known to cause discontinuities in chemical trends going down the pnictogen series. The potential for anomalous behavior arising from relativistic effects provides further motivation for the creation and investigation of new bismuth-based intermetallic compounds.

The extrapolated zero-pressure unit cell lengths obtained from the axial compressibility plots are $a_0 = 6.98(2) \text{ \AA}$ and $c_0 = 5.666(4) \text{ \AA}$. We can use these values to estimate the structural parameters under ambient conditions, which then allows us to compare structural parameters with other reported solid-state structures. One parameter that we are particularly interested in is the Fe–Bi distance. Fe–Bi bonds are, to the best of our knowledge, completely absent from solid-state materials. The extrapolated zero-pressure Fe–Bi distance in FeBi_2 is 2.96 \AA . At the elevated pressure of 29.9(1) GPa, the Fe–Bi bond distance in FeBi_2 is 2.719(2) \AA .

Based on the structural metrics and examination of the pnictide literature, we hypothesize that two driving forces behind the formation of the phase are the pressure-induced stabilization of the Fe–Bi bond and the intercolumn Bi–Bi bonding interaction (Figure 3). The numerous examples of compounds featuring Bi–Bi bonds across the solid-state and molecular literature bolster our supposition that creating stronger bonding interactions between pairs of bismuth atoms is a stabilizing factor. Indeed, this may serve as a design principle for the synthesis of additional bismuth based phases. As the pressure is decreased, the stabilizing influence of these bonds is expected to diminish until eventually phase separation (decomposition) becomes the thermodynamically favored process. Therefore, one possible explanation for the loss of the diffraction pattern of the compound below 2.9(1) GPa at room temperature is that, at this pressure, ambient temperature provides sufficient thermal energy to enable decomposition of the metastable phase. Future work will explore the quenchability of this phase at low temperatures, and with slow gas membrane decompression, since the rate of pressure release is

known to be an important factor in quenching metastable phases.^{37–39}

CONCLUSIONS

We synthesized the first compound in the iron–bismuth system, which also features the first Fe–Bi bond in the solid state. This compound persists down to at least 2.9(1) GPa, offering the potential for future quenchability. Ongoing work is focused on the scale-up of this reaction with a unique, highly specialized press capable of reaching the required pressures in order to enable studies of the electronic properties of this fascinating new material.

The results reported here ignite promise for new discoveries within the iron pnictide systems, and demonstrate the value of high pressure as a viable route toward new intermetallic compounds, and indeed toward creating new bonds in the solid state. In particular, the stabilizing effect of the Bi–Bi interaction within this compound offers significant promise for the high-pressure synthesis of iron–bismuth superconductors within the ThCr_2Si_2 structure type. Simple visual inspection of the Bi–Bi distances in the known BaMn_2Bi_2 structure hints that high pressure could be an appropriate vector to synthesize the iron analogue. Future work will focus on completing the series of pnictide superconductors via high-pressure synthesis.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acscentsci.6b00287.

Experimental details, Rietveld refinement parameters, and cell parameters used for BM3 fits (PDF)
Crystallographic information for FeBi_2 (CIF)

AUTHOR INFORMATION

Corresponding Author

*E-mail: danna.freedman@northwestern.edu.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We thank Dr. Ross Hrubciak for help with the temperature analysis. This research was initiated with DARPA funding (W911NF15100069) and executed with AFOSR funding (FA95501410358). S.M.C. acknowledges support from the NSF GRFP (DGE-1324585). S.D.J acknowledges support from the NSF (DMR-1508577), the Carnegie/DOE Alliance Center (CDAC), and the David and Lucile Packard Foundation. This work was performed at HPCAT (Sector 16), Advanced Photon Source (APS), Argonne National Laboratory. HPCAT operations are supported by DOE-NNSA under Award No. DE-NA0001974 and DOE-BES under Award No. DE-FG02-99ER45775, with partial instrumentation funding by NSF. The Advanced Photon Source is a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

REFERENCES

(1) Hosono, H.; Tanabe, K.; Takayama-Muromachi, E.; Kageyama, H.; Yamanaka, S.; Kumakura, H.; Nohara, M.; Hiramatsu, H.; Fujitsu, S. Exploration of new superconductors and functional materials, and

fabrication of superconducting tapes and wires of iron pnictides. *Sci. Technol. Adv. Mater.* **2015**, *16*, 033503.

(2) Xu, J.; Chen, J.; Jiang, G.; Song, B.; Han, Q. Dissolution equilibrium of Bi vapour in liquid Fe and influence of Ni and Mn. *Acta Metall. Sin.* **1993**, *29*, 65–68.

(3) Klement, W.; Jayaraman, A.; Kennedy, G. C. Phase diagrams of arsenic, antimony, and bismuth at pressures up to 70 kbars. *Phys. Rev.* **1963**, *131*, 632–637.

(4) Akahama, Y.; Kawamura, H.; Singh, A. K. Equation of state of bismuth to 222 GPa and comparison of gold and platinum pressure scales to 145 GPa. *J. Appl. Phys.* **2002**, *92*, 5892–5897.

(5) Tencé, S.; Janson, O.; Krellner, C.; Rosner, H.; Schwarz, U.; Grin, Y.; Steglich, F. CoBi₃—the first binary compound of cobalt with bismuth: high-pressure synthesis and superconductivity. *J. Phys.: Condens. Matter* **2014**, *26*, 395701.

(6) Clarke, S. M.; Walsh, J. P. S.; Amsler, M.; Malliakas, C. D.; Yu, T.; Goedecker, S.; Wang, Y.; Wolverton, C.; Freedman, D. E. Discovery of a superconducting Cu–Bi intermetallic compound by high-pressure synthesis. *Angew. Chem., Int. Ed.* **2016**, *55*, 13446–13449.

(7) Markovic, B.; Zivkovic, D.; Vrest' al, J.; Manasijevic, D.; Minic, D.; Talijan, N.; Stajic Trosic, J.; Todorovic, R. Experimental study and thermodynamic remodeling of the Bi–Cu–Ni system. *CALPHAD: Comput. Coupling Phase Diagrams Thermochem.* **2010**, *34*, 294–300.

(8) Ishida, K.; Nishizawa, T. *Binary Alloy Phase Diagrams*, 2nd ed.; Massalski, T. B., Ed.; ASM International: New York, 1990; Vol. 1, pp 725–728.

(9) Boa, D.; Hassam, S.; Kra, G.; Kotchi, K.; Rogez, J. The ternary bismuth–iron–antimony system: Experimental phase diagram study and thermodynamic evaluation. *CALPHAD: Comput. Coupling Phase Diagrams Thermochem.* **2008**, *32*, 227–239.

(10) Fei, Y.; Bertka, C. The interior of Mars. *Science* **2005**, *308*, 1120–1121.

(11) Speziale, S.; Zha, C.-S.; Duffy, T. S.; Hemley, R. J.; Mao, H.-K. Quasi-hydrostatic compression of magnesium oxide to 52 GPa: Implications for the pressure-volume-temperature equation of state. *J. Geophys. Res.: Solid Earth* **2001**, *106*, 515–528.

(12) Coelho, A. A. *TOPAS Academic: General Profile and Structure Analysis Software for Powder Diffraction Data*; Bruker AXS: Karlsruhe, Germany, 2007.

(13) Poffo, C. M.; Souza, S. M.; Trichês, D. M.; de Lima, J. C.; Grandi, T. A.; Polian, A.; Gauthier, M. Structural and optical studies of FeSb₂ under high pressure. *Phys. B* **2012**, *407*, 4686–4694.

(14) Wallbaum, H. J. Über A₂B-Verbindungen vom Al₂Cu-typ. *Z. Metallk.* **1943**, *35*, 218–221.

(15) Kuz'ma, Yu. B.; Markiv, V.; Ya; Voroshilov, Yu. V.; Skolozdra, R. V. X-ray structural investigations of some alloys of the Zr–Fe and Zr–Co systems. *Inorg. Mater.* **1966**, *2*, 222–225.

(16) Nowotny, H.; Funk, R.; Pesl, J. Crystallochemical investigation of the systems Mn–As, V–Sb, Ti–Sb. *Monatsh. Chem.* **1951**, *82*, 513–525.

(17) Rosenqvist, T. Magnetic and crystallographic studies on the higher antimonies of iron, cobalt and nickel. *Acta Metall.* **1953**, *1*, 761–763.

(18) Peacock, M. A.; Dadson, A. S. On Rammelsbergite and Pararammelsbergite: Distinct forms of nickel diarsenide. *Am. Mineral.* **1940**, *25*, 561–577.

(19) Takizawa, H.; Uheda, K.; Endo, T. A new ferromagnetic polymorph of CrSb₂ synthesized under high pressure. *J. Alloys Compd.* **1999**, *287*, 145–149.

(20) Lips, F.; Dehnen, S. Neither electron-precise nor in accordance with Wade–Mingos rules: The ternary cluster anion [Ni₂Sn₇Bi₅]³⁻. *Angew. Chem., Int. Ed.* **2011**, *50*, 955–959.

(21) Cassidy, J. M.; Whitmire, K. H. Syntheses and structures of the phenylbismuth/transition-metal carbonyl compounds [PPN]-[Ph₂BiFe(CO)₄], (Ph₂Bi)₂Fe(CO)₄, [PhBiFe(CO)₄]₂ and Ph₂BiMn(CO)₅. *Inorg. Chem.* **1991**, *30*, 2788–2795.

(22) Wolf, R.; Fischer, J.; Fischer, R. C.; Fetting, J. C.; Power, P. P. Reactions of terphenylbismuth dihalides with KSi(SiMe₃)₃,

K₂Si₂(SiMe₃)₄ and Na₂[Fe(CO)]₄: Reduction vs. metathesis. *Eur. J. Inorg. Chem.* **2008**, 2515–2521.

(23) Shieh, M.; Liou, Y.; Hsu, M.-H.; Chen, R.-T.; Yeh, S.-J.; Peng, S.-M.; Lee, G.-H. A unique bismuth–iron chain polymer containing the…–Bi–Fe… link: Formation and structure of [BuBiFe(CO)₄]_∞. *Angew. Chem., Int. Ed.* **2002**, *41*, 2384–2386.

(24) James, A. M.; Lord, M. P. *Macmillan's Chemical and Physical Data*; Macmillan Press: London, 1992.

(25) Gascoin, F.; Sevov, S. C. Synthesis and characterization of A₃Bi₂ (A = K, Rb, Cs) with isolated diatomic dianion of bismuth, [Bi₂]²⁻, and an extra delocalized electron. *J. Am. Chem. Soc.* **2000**, *122*, 10251–10252.

(26) Brese, N. E.; von Schnering, H. G. Bonding trends in pyrites and a reinvestigation of the structures of PdAs₂, PdSb₂, PtSb₂ and PtBi₂. *Z. Anorg. Allg. Chem.* **1994**, *620*, 393–404.

(27) Zhdanov, G. S.; Zhuravlev, N. N.; Kuz'min, R. N. Study of the system Bi–Rh. *Russ. J. Inorg. Chem.* **1958**, *3*, 287–297.

(28) Xu, L.; Bobev, S.; El-Bahraoui, J.; Sevov, S. C. A naked diatomic molecule of bismuth, [Bi₂]²⁻, with a short Bi–Bi bond: synthesis and structure. *J. Am. Chem. Soc.* **2000**, *122*, 1838–1839.

(29) Calderazzo, F.; Morvillo, A.; Pelizzi, G.; Poli, R. Synthesis and crystal and molecular structure of tetraphenyldibismuthine, Bi₂Ph₄, the first crystallographically characterized tetraorganyl derivative of bismuth(II). *J. Chem. Soc., Chem. Commun.* **1983**, *9*, 507–508.

(30) Tokitoh, N.; Arai, Y.; Okazaki, R.; Nagase, S. Synthesis and characterization of a stable dibismuthene: Evidence for a Bi–Bi double bond. *Science* **1997**, *277*, 78–80.

(31) Twamley, B.; Sofield, C. D.; Olmstead, M. M.; Power, P. P. Homologous series of heavier element dipnictenes 2,6-Ar₂H₃C₆E = EC₆H₃-2,6-Ar₂ (E = P, As, Sb, Bi; Ar = Mes = C₆H₂-2,4,6-Me₃; or Trip = C₆H₂-2,4,6-ⁱPr₃) stabilized by *m*-terphenyl ligands. *J. Am. Chem. Soc.* **1999**, *121*, 3357–3367.

(32) Clegg, W.; Compton, N. A.; Errington, R. J.; Fisher, G. A.; Norman, N. C.; Marder, T. B. Dibismuth as a four-electron donor ligand. Synthesis and molecular and electronic structure of [M₂(CO)₄(η-C₅H₄Me)₂(μ-η²-Bi₂)] (M = Mo or W). *J. Chem. Soc., Dalton Trans.* **1991**, 2887–2895.

(33) Adams, R. D.; Pearl, W. C., Jr. Rhenium–bismuth carbonyl cluster compounds. *Inorg. Chem.* **2009**, *48*, 9519–9525.

(34) Wu, X.; Steinle-Neumann, G.; Qin, S.; Kanzaki, M.; Dubrovinsky, L. Pressure-induced phase transitions of AX₂-type iron pnictides: An ab initio study. *J. Phys.: Condens. Matter* **2009**, *21*, 185403.

(35) Angel, R. J.; Alvaro, M.; Gonzalez-Platas, J. EosFit7c and a Fortran module (library) for equation of state calculations. *Z. Kristallogr. - Cryst. Mater.* **2014**, *229*, 405–419.

(36) Pyykko, P. Relativistic effects in structural chemistry. *Chem. Rev.* **1988**, *88*, 563–594.

(37) Wentorf, R. H.; Kasper, J. S. Two new forms of silicon. *Science* **1963**, *139*, 338–339.

(38) Crain, J.; Ackland, G. J.; Maclean, J. R.; Piltz, R. O.; Hatton, P. D.; Pawley, G. S. Reversible pressure-induced structural transitions between metastable phases of silicon. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1994**, *50*, 13043–13046.

(39) Zhao, Y.-X.; Buehler, F.; Sites, J. R.; Spain, I. L. New metastable phases of silicon. *Solid State Commun.* **1986**, *59*, 679–682.